



CVD Zinc Sulfide[®] | Cleartran[®]
VIS/IR applications




CVD Zinc Sulfide® | Cleartran®

CVD Ceramics' chemically vapor deposited CVD Zinc Sulfide® is the low cost alternative for infrared windows, domes and optical elements. With a fracture strength double that of zinc selenide and high hardness, zinc sulfide has been used successfully in many military applications requiring mechanical resistance to hostile environments. Cleartran® is a form of CVD Zinc Sulfide® material that is modified by a post-deposition hot isostatic process. This process removes zinc hydrides from the crystal lattice, normalizes crystal structure and purifies the material, all contributing to single crystal-like transmittance in the visible through far infrared ranges (0.35 -14 microns). With its low absorption and scatter throughout its broad transmitting range and high optical quality, it is particularly well-suited for multi-spectral applications that require a single aperture for beam path for several wavebands.

CVD Zinc Sulfide® and Cleartran® are chemically inert, non-hygroscopic, highly pure, theoretically dense and easily machined.

Custom diameters, rectangles, CNC-profiled blanks, generated lens blanks, prisms and near-net shape domes can be made to your specifications.

Spectral Transmission CVD Zinc Sulfide® and Cleartran®

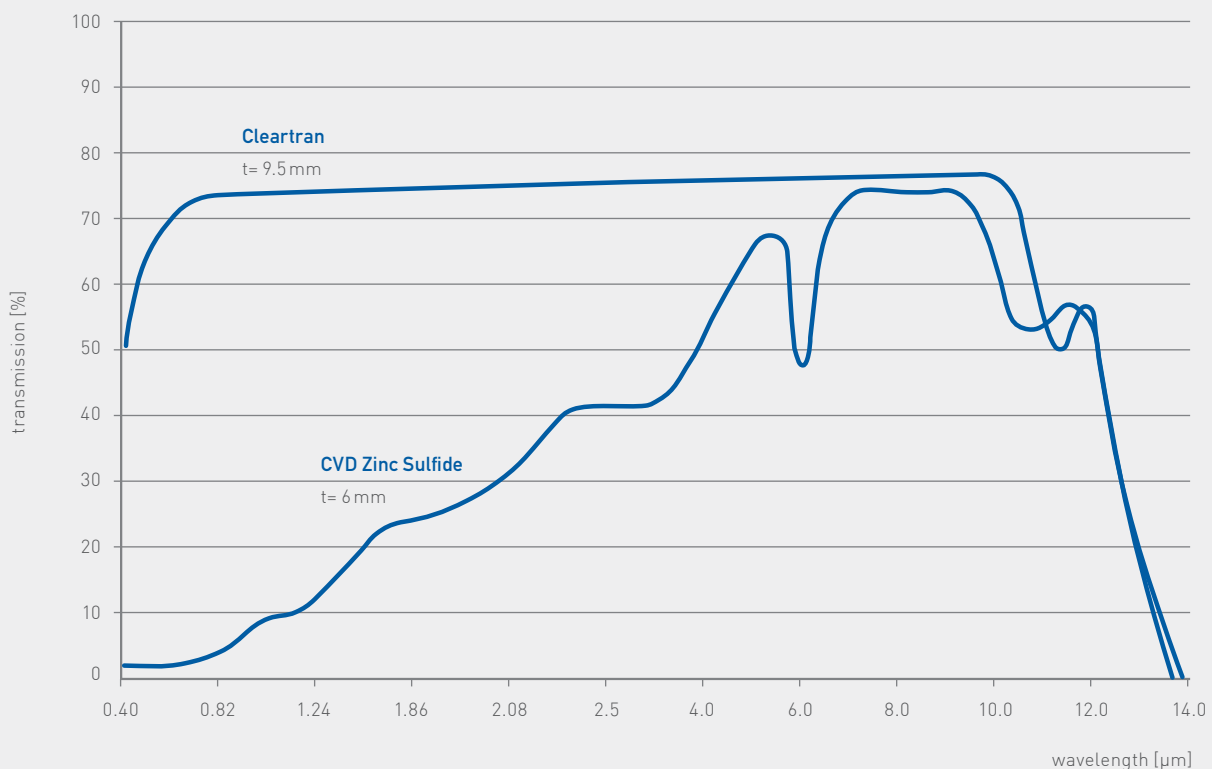

Properties of CVD Zinc Sulfide® and Cleartran®

	Zinc Sulfide	Cleartran
Optical properties		
10% transmission limits (t=6mm)	1.0µm – 14µm	0.37µm – 14µm
Index of refraction inhomogeneity ($\Delta n/n$)	<100ppm @10.6µm	<20ppm @633nm
Thermo-optic coefficient dn/dT (298-358K)		
K ⁻¹ @ 0.6328µm		5.43×10^{-5}
K ⁻¹ @ 1.15 µm	4.6×10^{-5}	4.21×10^{-5}
K ⁻¹ @ 3.39µm	4.3×10^{-5}	3.87×10^{-5}
K ⁻¹ @ 10.6µm	4.1×10^{-5}	
Bulk absorption coefficient		
cm ⁻¹ @ 1.3µm		6.0×10^{-4}
cm ⁻¹ @ 2.7µm		1.0×10^{-3}
cm ⁻¹ @ 3.8µm		6.0×10^{-4}
cm ⁻¹ @ 9.27µm		6.0×10^{-3}
cm ⁻¹ @ 10.6µm	2.0×10^{-1}	2.0×10^{-1}

Mechanical properties		
Hardness: Knoop, 50g load [kg mm ⁻²] Vickers, 1kg load [kg mm ⁻²]	200-235 230	160 150
Flexural strength (modulus of rupture) 4pt. loading [psi] 4pt. loading [MPa] Disc bursting [MPa]	15×10^3 103 84	1.09×10^4 75 50
Fracture toughness (critical stress intensity factor, K _{IC} values) [MPa \sqrt{m} , Vickers, 1kg]	0.8	1.0
Young's modulus [psi] [GPa]	10.8×10^6 74.5	10.8×10^6 74.5
Poisson's ratio	0.29	0.28

	Zinc Sulfide	Cleartran
Physical properties		
Crystal structure	cubic	cubic
Grain size	2-8µm	20-35µm
Density [g cm ⁻³] @298K	4.09	4.09
Resistivity [Ω cm]	$\sim 10^{12}$	$\sim 10^{13}$
Chemical purity [%]	99.996	99.9996

Thermal properties		
Coefficient of Thermal Expansion [K ⁻¹] @273K [K ⁻¹] @373K [K ⁻¹] @473K [K ⁻¹] @208-573K	6.6×10^{-6} 7.3×10^{-6} 7.7×10^{-6}	6.3×10^{-6} 7.0×10^{-6} 7.5×10^{-6} 6.5×10^{-6}
Thermal conductivity [JK ⁻¹ m ⁻¹ s ⁻¹] @298K	16.7	28.4
Heat capacity [Jg ⁻¹ K ⁻¹] @298K [Jg ⁻¹ K ⁻¹] @273K [Jg ⁻¹ K ⁻¹] @323K [Jg ⁻¹ K ⁻¹] @373K	0.469	0.474 0.489 0.504
Thermal diffusivity [m ² s ⁻¹]		1.46×10^{-5}

Indices of refraction		
Wavelength [µm]	n	n
0.4358	2.48918	2.48918
0.6438	2.34731	2.34731
1.0140	2.29165	2.29165
2.0581	2.26442	2.26442
3.0	2.25772	2.25772
4.0	2.25231	2.25231
5.0	2.24661	2.24661
8.0	2.22334	2.22334
9.0	2.21290	2.21290
10.0	2.20084	2.20084
12.0	2.17101	2.17101
13.0	2.15252	2.15252

North America



CVD Ceramics, Inc.
11911 Advanced Materials Drive
New Iberia, LA 70560
USA
phone + 1 337 867 4263 Ext. 2238
fax + 1 337 867 4494
info@cvdceramics.com
www.cvdceramics.com

For inquiries
please contact
our local Sales
Representative

United Kingdom

Ms Carolyne Ockendon
Hellma UK Ltd.
phone + 44 1702 335 266
fax + 44 1702 430 652
sales.uk@hellma.com

Japan

Mr Koichi Inaba
Hellma Materials GmbH
Japan Branch Office
phone + 81 45 440 6617
fax + 81 45 440 6001
mobile + 81 80 5468 9356
koichi.inaba@hellma.com

France

Mr Bernard Weill
Hellma France S.A.R.L.
phone + 33 1 42 08 01 28
fax + 33 1 42 08 13 65
info.fr@hellma.com

Israel

Mr Coby Cohen
Shoshic Technologies Ltd.
phone + 972 77 9100 875
fax + 972 544 399 862
coby@stech.co.il

For inquiries
please contact
our local
Distributor

Germany

Hellma Materials GmbH
Moritz-von-Rohr-Straße 1
07745 Jena / Germany
phone + 49 3641 2877-0
fax + 49 3641 2877-200
info.materials@hellma.com
www.hellma-materials.com